



Air-Drying One Component Anti-Corrosion Primer - Grey

Starting Point Formulation
with Borchi® Gen 1750 & Bayhydrol UH 2592


Dry Times - Under 1.5 Hours
Even Under Adverse Conditions

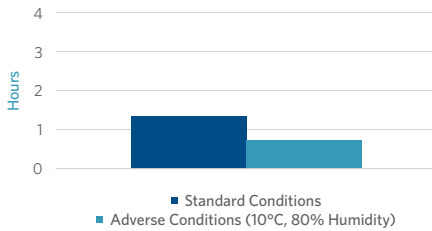

Great Corrosion Resistance
Q-FOG Salt Spray After 500 hours

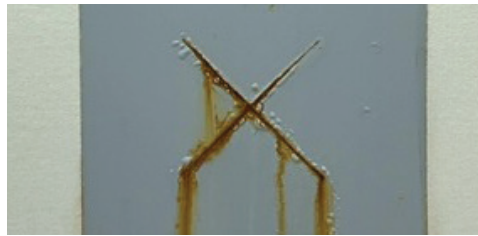

Excellent Pendulum Hardness
(König Method)

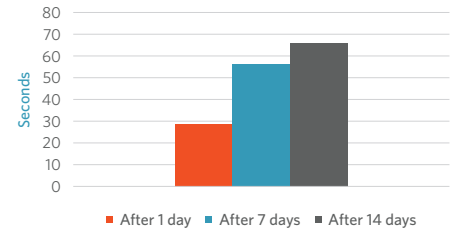

Air-Drying One Component Anti-Corrosion Primer - Grey

Step	Instructions	Components	% by WT.	Supplier	Function
1	Place in vessel	Bayhydrol UH 2592	30.84	Covestro	Resin
2	Add organic solvents, each fluid additives under agitation	Butyl glycol/Dowanol DPnB (1:1) Borchi® Gen 1750 Ascotran H10 Borchi® Gol LA 50 Borchers® AF 1171	3.70 1.00 0.17 0.10 0.10	Sigma Aldrich Borchers GmbH Ascotec Borchers GmbH Borchers GmbH	Solvent Wetting & Dispersing Flash rust inhibitor Substrate wetting Defoamer
3	Active anti-corrosion pigments and zinc oxide should be dispersed with the additives and solvents into the resins for approx. 5 min. at 2000 rpm	K-White 105 Bayoxide® Z active	8.28 0.82	Lehmann & Voss Borchers GmbH	Anti-corrosion, white pigment Corrosion protection pigment
4	Add water and stir	Deionized Water	1.58		
5	Slowly add EDIPA and stir for 5 minutes	N-Ethyl-diisopropylamine 50%ig in Ethanol	0.50	Sigma Aldrich	Neutralizing agent
6	Add water and stir for 5 minutes	Deionized Water	0.60		
7	Incorporate the remaining pigments and extenders with dissolver. Disperse for 20 min at 3000 rpm	Kronos 2190 Lamp Black FW 101 EWO Finntalc M 15	9.26 0.10 5.89 3.54	Kronos Titan Orion Engineered Carbons Sachtleben minerals Elementis	Pigment Pigment Extender Extender
8	Grind in a bead mill up to a grain size of <20 µm				
9	Add water and stir for 5 minutes	Deionized Water	1.40		
10	Let down the mill base with the resin, stir for 10 minutes at 1000 rpm	Bayhydrol UH 2592	30.84	Covestro	Resin
11	Add the thickener and stir for 10 minutes at 1000 rpm	Borchi® Gel 0620, 10% in Butyl glycol	0.88	Borchers GmbH	Rheology Modifier
12	Add the drier and stir again for 10 minutes at 500 rpm	Borchi® OXY-Coat 1101	0.40	Borchers GmbH	Co-free drier
		Total	100.00		
13	Add water to set recommended spray viscosity: flow time of 25-30 s in DIN 4 cup.		9.00		
		Total	109.00		

Order your sample at:
www.borchers.com/contact

PLEASE NOTE: As each customer's use of our product may be different, information we provide, including without limitation, recommendations, test results, samples, care/labeling/processing instructions or marketing advice, is provided in good faith but without warranty and without accepting any responsibility/liability. Each customer must test and be responsible for its own specific use, further processing, labeling, marketing, etc. All sales are exclusively subject to our standard terms of sale posted at www.milliken.com/terms (all additional/different terms are rejected) unless explicitly agreed otherwise in a signed writing. Borchi is a registered trademark of Borchers GmbH.